

Estimate of uniaxial compressive strength and Young's modulus of the elasticity of natural stone Giallo d'Istria

Briševac, Zlatko; Hrženjak, Petar; Cotman, Ivan

Source / Izvornik: **ISRM European Rock Mechanics Symposium (EUROCK 2017), 2017, 191, 434 - 441**

Conference paper / Rad u zborniku

Publication status / Verzija rada: **Published version / Objavljena verzija rada (izdavačev PDF)**

<https://doi.org/10.1016/j.proeng.2017.05.201>

Permanent link / Trajna poveznica: <https://urn.nsk.hr/urn:nbn:hr:169:559436>

Rights / Prava: [Attribution-NonCommercial-NoDerivatives 4.0 International/Imenovanje-Nekomercijalno-Bez prerada 4.0 međunarodna](#)

Download date / Datum preuzimanja: **2025-03-10**



Repository / Repozitorij:

[Faculty of Mining, Geology and Petroleum Engineering Repository, University of Zagreb](#)





Symposium of the International Society for Rock Mechanics

Estimate of Uniaxial Compressive Strength and Young's Modulus of the Elasticity of Natural Stone Giallo d'Istria

Zlatko Briševac^{a,*}, Petar Hrženjak^a, Ivan Cotman^b

^aUniversity of Zagreb's Faculty of Mining, Geology and Petroleum Engineering, Pierottijeva 6, 10000 Zagreb, Croatia

^bKamen d.d. (PLC) Pazin Trg slobode 2, 52000 Pazin, Croatia

Abstract

The famous natural stone Giallo d'Istria, is categorized as a thick-bedded biomicritic limestone, is exploited in three locations on the Croatian peninsula of Istria. In order to detect high-quality areas of the existing quarries and some new areas of exploitation as well, models have been developed for the purpose of estimating important physico-mechanical properties of this limestone. The models are based on the results of many laboratory tests. Complex and simple estimation models have been mutually compared. The modelling is based on neural networks and multiple and simple regressions. Special attention was paid to the applicability of the developed models in other sites.

© 2017 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Peer-review under responsibility of the organizing committee of EUROCK 2017

Keywords: Uniaxial compressive strength; Young's modulus of the elasticity; estimation; Giallo d'Istria; neural network; simple regression

1. Introduction

Giallo d'Istria (yellow Istrian) is the general name for the natural stone from the Kanfanar, Selina and Korenići quarries which are situated on the Croatian peninsula of Istria. Stratigraphically speaking, Giallo d'Istria is a Lower Cretaceous biomicritic limestone (see Figure 1). These deposits are characterized by a thick-bedded limestone of a yellowish color. The thickness of the individual layers is anywhere from 0.80 to 1.50 m, provided that they are separated with contour lines that define the boundaries and mark the weakly bound contour lines.

* Corresponding author. Tel.: +385-01-5535-864; fax: +385-01-5535-860.
E-mail address: zlatko.brisevac@rgn.hr

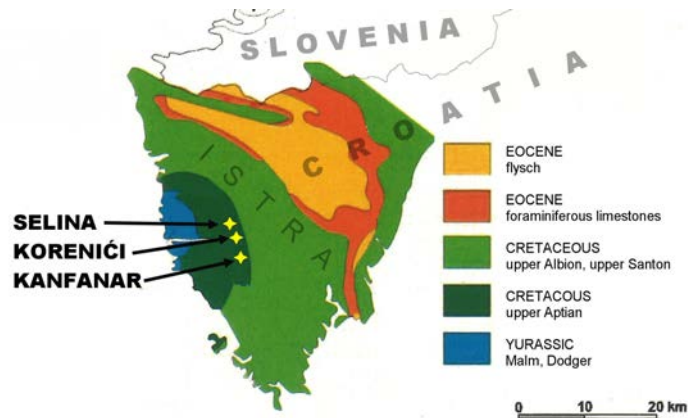


Fig. 1. Position of the quarrys.

The thickness of the overburden is 17 to 25 m, which layers are typically denoted alphabetically as shown in Figure 2, and the exploitation layers have a thickness between 4.8 and 6.8 meters, and sometimes even up to 7.6 m they are marked with Roman numerals I, II, IV, V and VI. The layers differ in appearance and structure, and thus cannot be mixed in the production process. There are also differences in the physico-mechanical properties even within the layers in its strikes and dips, especially in porosity and density. In exploitation, such areas must be rejected, and thus losses in yield occur [1, 2, 3].

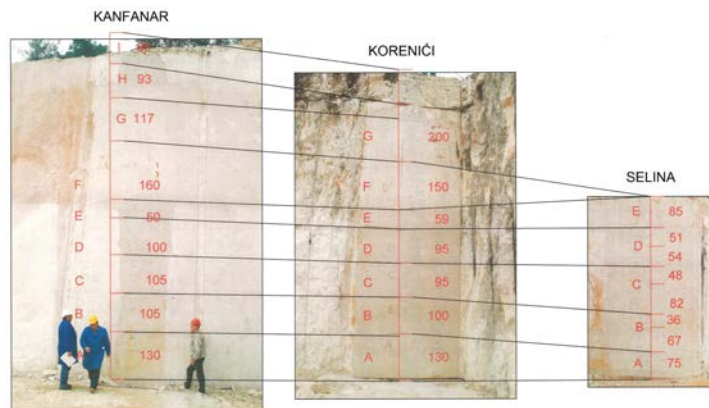


Fig. 2. The spatial distribution of overburden layers in quarries Kanfanar, Korenići and Selina.

In order to ensure a uniform quality of exploited natural stone, it is necessary, and if feasible, as simply as possible, to locate areas where there are distinct changes in the strength and deformability of materials. For this reason, a need arose to find a method which could practically assess the uniaxial compressive strength (UCS) and Young's modulus of elasticity (E) based on easily determined material characteristics. Extensive testing of natural stone for the development and introduction of underground mining in quarries [4] took place and the physical and mechanical properties of the individual layers were tested which advanced the progress in achieving this goal. The implemented tests, among other things, enabled the determination of the interdependence between the various physico-mechanical characteristics. Modelling in this paper was inspired by the methods of assessing physico-mechanical characteristics published in scientific literature. Principally, the most widely used is regression, but recently more sophisticated techniques such as neural networks have frequently been applied as well [5].

Among scientific papers, those which use similar parameters on the basis of which UCS and E are determined should be emphasized: Palchik and Hatzor [6], Tugrul [7], Tziallas et al. [8], Yagiz [9], Moradian, and Behnia [10], Manouchehrian et al. [11], Dehghan [12], Gokceoglu and Zorlu [13], Karakus and Tutmez [14], Yilmaz and Yuksek [15] and Dehghan et al. [16].

2. Performed testing

Due to the need of the detailed determination of the physico-mechanical properties of materials from all the representative layers of deposits, laboratory tests were conducted on several occasions during the research period. All basic laboratory tests were carried out according to the recommended methods (Suggested Methods) International Society for Rock Mechanics. The following tests were performed: determining the density and porosity of materials [17]; testing the uniaxial compressive strength (UCS) and deformability of materials [18]; determining the velocity of ultrasonic elastic P-waves (P-velocity) [19]; determining the point load strength index (PLT) [20] and determining Schmidt hammer Rebound Hardness (SRH) [21]. The basic sample preparation was conducted by employees of the company Kamen d.d. (PLC) Pazin, and this preparation consisted of the selection of large blocks at the quarry and preparing smaller blocks and samples at the mill. So they prepared small blocks measuring $23 \times 30 \times 23$ cm layer of overburden F and E from Korenić, D and A from Selina, C and B from Kanfanar where they also extracted samples for testing exploitation layers I, II, IV, V and VI. Laboratory samples were later extracted from such small blocks and analyzed according to the requirements of individual test methods. Sample preparation for individual tests as well as their testing was conducted in the Geomechanical Laboratory at the Faculty of Mining, Geology and Petroleum Engineering, University of Zagreb. Part of the preparation as well as the geological determination of materials was carried out in the Laboratory of Engineering Geology at the Croatian Geological Survey institute in Zagreb [21]. The results of the tests are shown in Table 1.

Table 1. Results of laboratory tests.

Place and layer	Limestone type	Density (1000 kg·m ⁻³)	Porosity (%)	PLT (MPa)	SRH	Vp (1000 m·s ⁻¹)	UCS (MPa)	E (GPa)
Korenić, layer F	Mudstone	2.164	16.46	2.1	51.4	4.424	33.1	43.647
Korenić, layer F	Mudstone	2.195	18.43	2.4	51.4	4.506	56.97	30.88
Korenić, layer E	Grainstone	2.379	10.94	1.7	38.2	5.107	51.44	38.379
Korenić, layer E	Grainstone	2.376	11.25	3.8	38.2	5.261	66.48	44.338
Selina, layer D	Floatstone	2.627	2.34	1.5	60	5.97	74.07	45.937
Selina, layer D	Floatstone	2.626	2.61	3.24	57	6.038	68.76	57.265
Selina, layer D	Floatstone	2.628	2.81	3.88	61.7	6.039	82.44	56.298
Selina, layer D	Floatstone	2.623	3.27	2.68	61.3	6.044	80.12	48.805
Selina, layer D	Floatstone	2.634	2.71	0.87	66.5	6.13	89.87	66.746
Kanfanar, layer C	Wackestone	2.64	3.06	4.4	63.5	5.983	129.93	58.074
Kanfanar, layer C	Wackestone	2.634	2.43	3.6	63	5.932	126.02	62.254
Kanfanar, layer C	Wackestone	2.638	2.67	3.9	68.5	5.992	136.1	57.682
Kanfanar, layer C	Wackestone	2.634	2.82	2.1	61	5.886	118.81	55.92
Kanfanar, layer C	Wackestone	2.634	2.29	3.7	59	5.88	109.75	54.787
Kanfanar, layer B	Packstone	2.652	2.12	4.77	63.5	6.098	148.39	44.862
Kanfanar, layer B	Packstone	2.652	2.49	3.76	61.1	5.976	133.41	65.552
Kanfanar, layer B	Packstone	2.653	2.3	3.91	63.5	6.067	154.2	64.756
Kanfanar, layer B	Wackestone	2.652	2.14	4.03	61	6.057	122.46	65.292
Selina, layer A	Floatstone	2.635	2.81	3.2	55	6.096	84.57	66.841
Selina, layer A	Floatstone	2.671	3.15	2.4	58.5	6.071	89.14	52.953
Selina, layer A	Floatstone	2.635	3.48	3.2	56	6.104	85.48	55.492
Selina, layer A	Floatstone	2.636	2.75	2.6	70	6.123	107.61	66.878
Selina, layer A	Floatstone	2.638	2.48	2.9	70	6.079	102.52	63.806
Kanfanar, layer I	Wackestone	2.675	1.75	4.64	55.5	5.884	109.68	51.835
Kanfanar, layer I	Wackestone	2.677	1.25	4.65	62.4	5.909	115.26	51.429
Kanfanar, layer I	Wackestone	2.676	1.23	3.81	66.5	5.896	121.27	52.118
Kanfanar, layer I	Mudstone	2.674	1.15	5.42	61.8	5.958	111.3	50.405
Kanfanar, layer I	Mudstone	2.673	1.13	5.3	66	5.955	121.17	55.2
Kanfanar, layer II	Floatstone	2.65	2.07	3.6	62	5.944	112.54	64.556
Kanfanar, layer II	Floatstone	2.654	2	3.2	60	5.829	99.11	61.59
Kanfanar, layer II	Floatstone	2.651	2.25	3.9	61	5.984	109.31	60.941

Table 1. Results of laboratory tests - continuation.

Place and layer	Limestone type	Density (1000 kg·m ⁻³)	Porosity (%)	PLT (MPa)	SRH	Vp (1000 m·s ⁻¹)	UCS (MPa)	E (GPa)
Kanfanar, layer II	Floatstone	2.666	2.02	3.6	67	5.97	136.26	68.11
Kanfanar, layer II	Floatstone	2.651	1.61	4.3	62	5.967	119.7	58.04
Kanfanar, layer IV	Wackestone	2.684	0.64	5.5	61.5	6.149	152.37	60.884
Kanfanar, layer IV	Mudstone	2.698	0.74	5.2	61	6.145	125.64	55.797
Kanfanar, layer IV	Mudstone	2.686	0.85	5.4	68.5	6.096	178.19	61.383
Kanfanar, layer IV	Mudstone	2.684	0.99	4.7	63.5	6.089	169.45	69.09
Kanfanar, layer IV	Wackestone	2.688	0.84	4.6	64.5	6.136	172.93	68.997
Kanfanar, layer V	Floatstone	2.68	1.8	4.8	59.5	6.149	136.43	67.917
Kanfanar, layer V	Rudstone	2.683	1.1	4.5	63	6.229	175.24	74.153
Kanfanar, layer V	Floatstone	2.684	1.16	3.7	69.5	6.221	180.5	67.262
Kanfanar, layer V	Floatstone	2.683	0.84	4.8	60	6.178	166.31	72.322
Kanfanar, layer V	Floatstone	2.683	0.84	4.9	60	6.15	168.22	68.397
Kanfanar, layer VI	Floatstone	2.613	1.13	3.2	67	5.919	107.52	61.541
Kanfanar, layer VI	Floatstone	2.607	1.23	3.5	63.5	5.897	75.84	65.258
Kanfanar, layer VI	Floatstone	2.601	1.5	4.8	51	5.857	72.18	65.612
Kanfanar, layer VI	Rudstone	2.629	1.28	4.3	66	5.971	90.74	66.786
Kanfanar, layer VI	Rudstone	2.624	1.15	4.8	67	5.978	102.15	86.48

The results of descriptive statistics of the set presented in Table 1 are given in Table 2. According to the size of the standard deviation, it is visible that the largest dispersion of data was given by the UCS test results, while on the other hand, the least dispersion of data was during the testing of the density and velocity of P waves. However, if we want to compare the dispersion of data for different values with different units of measurement, then the Coefficient of variation is accurate. It shows the greatest dispersion with porosity, and two property groups have approximately the same dispersion. The first group consists of UCS and PLT, and the second group consists of density, SRH and P-velocity.

Table 2. Descriptive statistics of the surveyed materials Giallo D Istria.

Comparative tests conducted	Mean value	Minimum value	Maximum value	Standard deviation	Coefficient of variation (%)
Density (1000 kg·m ⁻³)	2.6215	2.1640	2.6980	0.11112	4.239
Porosity (%)	2.9242	0.6400	18.4300	3.66629	125.378
Point load test – PLT (MPa)	3.7867	0.8700	5.5000	1.09370	28.883
Schmidt Rebound Hardness - SRH	61.0208	38.2000	70.0000	6.63633	10.876
P-wave velocity (1000 m·s ⁻¹)	5.9234	4.4240	6.2290	0.36506	6.163
Uniaxial compressive strength – UCS (MPa)	114.1865	33.1000	180.5000	35.86063	31.405
Young's modulus of elasticity – E (GPa)	59.4489	30.8800	86.4800	9.99195	16.808

The correlation dependence of individual tests is shown in Table 3. Porosity has a negative correlation with all other properties, which means an increase in the porosity results in a reduction in all other values. According to Evans' interpretation [22] the strength of interdependencies can be described by size, as shown in Table 3.

Table 3. Correlations between tests performed.

Comparative tests conducted	Density (1000 kg·m ⁻³)	Porosity (%)	PLT (MPa)	SRH	Vp (1000 m·s ⁻¹)	UCS (MPa)	E (GPa)
Density (1000 kg·m ⁻³)	1.000000	-0.975333	0.459429	0.640282	0.965444	0.649812	0.594591
Porosity (%)	-0.975333	1.000000	-0.482353	-0.653525	-0.942704	-0.600888	-0.652219
PLT (MPa)	0.459429	-0.482353	1.000000	0.222391	0.384955	0.603924	0.336280
SRH	0.640282	-0.653525	0.222391	1.000000	0.628970	0.561293	0.543868
P-velocity (1000 m·s ⁻¹)	0.965444	-0.942704	0.384955	0.628970	1.000000	0.621141	0.646761
UCS (MPa)	0.649812	-0.600888	0.603924	0.561293	0.621141	1.000000	0.522603
E (GPa)	0.594591	-0.652219	0.336280	0.543868	0.646761	0.522603	1.000000

Porosity has a very strong interdependence with density and P-velocity. UCS has a strong correlation with density, porosity, PLT and P-velocity. E has a strong correlation with porosity and P-velocity, a weak interdependence with PLT, and it has a moderate relationship with the rest of the properties. The geological determination of samples shows that the test samples were mostly with mud and matrix supported and belonging to madstone, wackstone and floatstone types per Dunham's classification limestone [23]. The appearance of grain-supported in the form of grainstone and packstone types occur in two layers of overburden, but also in the deepest layers marked V and VI where there were three samples of the rudstone type.

3. Modelling estimates

The most accessible method for assessing UCS and E are simple and multiple regression as well as neural networks and so modelling in this paper was based on those procedures. For modelling complex assessments, the software package Statistica 12 was used, which offers the possibility of creating regression models and the models of artificial neural networks such as Multiple Layer Perceptron (MLP). This type of network was chosen because it performed better than the other type which Statistica 12 can produce, i.e. Radial Basis Function (RBF).

3.1. Simple regression models

Simple regression equations comprise relations defined for the estimation of UCS and E values as dependent variables based on the tested value of another property that constitutes an independent variable [24]. In this paper, the independent variable was represented by one of the values for testing density, porosity, PLT, SRH and P-velocity. The success of the model is usually determined through the coefficient of determination R^2 . The modelling results are shown in Table 4. Among all the performed simple models, the best models for estimating UCS are shown in equations (1) (2) and (3) which used density, porosity and SRH as independent variables. The best models for estimating E are shown in equations (4) and (5) which used porosity and P-velocity as independent variables.

$$UCS = 0,1724 \cdot e^{2,4567 \cdot \rho} \quad (1)$$

$$UCS = 139,63 \cdot n^{-0,36} \quad (2)$$

$$UCS = 1,5991 \cdot e^{0,7112 \cdot v_p} \quad (3)$$

$$UCS = 65,025 \cdot e^{-0,036 \cdot n} \quad (4)$$

$$UCS = 7,1465 \cdot e^{0,3551 \cdot v_p} \quad (5)$$

where is: UCS - uniaxial compressive strength in MPa, E - Young's modulus of elasticity in GPa, ρ - density in $1000 \text{ kg} \cdot \text{m}^{-3}$, n - porosity in %, v_p - P-wave velocity in $1000 \text{ m} \cdot \text{s}^{-1}$.

Table 4. Simple models for estimation UCS and E.

Dependent variable	Independent variable	Coefficient of determination R^2
UCS	Density	0.5959
UCS	Porosity,	0.5703
UCS	PLT	0,3711
UCS	SRH	0,3885
UCS	P velocity	0.5391
E	Density	0.4427

Table 4. Simple models for estimation UCS and E- continuation.

Dependent variable	Independent variable	Coefficient of determination R ²
E	Porosity	0.5201
E	PLT	0.1226
E	SRH	0.3271
E	P-velocity	0.5045

3.2. Multi regression models

Multiple regression models are represented by the equation (6).

$$Y = \beta_0 + \beta_1 X_1 + \beta_2 X_2 + \dots + \beta_i X_k + \varepsilon \quad (6)$$

where is: Y - dependent variable, X_1, X_2, \dots, X_k - independent variables, β_i - denotes contribution of the independent variable X_i , ε - random error.

According to Table 5, which presents the results of modelling, the model that included porosity, PLT, SRH and P-velocity proved to be the best for estimating UCS. The estimation of E using this type of model did not show greater success than the model based on single regressions.

Table 5. Multiple regression models.

Dependent variable	Independent variable	Coefficient of determination R ²
UCS	Density, PLT, SRH	0.5918
UCS	Porosity, PLT, SRH	0.5656
UCS	PLT, SRH, P-velocity	0.5952
UCS	Density, PLT	0.5405
UCS	Density, SRH	0.4580
UCS	Porosity, PLT	0.4896
UCS	Porosity, SRH	0.4107
UCS	PLT, P-velocity	0.5421
UCS	SRH, P-velocity	0.4340
E	Density, PLT, SRH	0.4075
E	Porosity, PLT, SRH	0.4518
E	PLT, SRH, P-velocity	0.4593
E	Density, PLT	0.3586
E	Density, SRH	0.3987
E	Porosity, PLT	0.4260
E	Porosity, SRH	0.4495
E	PLT, P-velocity	0.4273
E	SRH, P-velocity	0.4494

3.3. Neural network models

The success of neural network models is shown in Table 6, where the best performance estimate of UCS is shown in the model in the first row of the table which has the largest number of available predictors. Based on performance, the second place model is the model in which the predictors were density, porosity, PLT and SRH, and

in third place is the model with the density and porosity predictors. Predictors of the third model can be determined by one simple procedure and so from that point of view, this model is very suitable for the estimation of UCS.

Table 6. Neural networks models.

Estimates target	Input parameters	Coefficient of determination R^2
UCS	Density, porosity, PLT, SRH, P-velocity	0.8565
UCS	Density, porosity, PLT, SRH	0.8015
UCs	Density, porosity, SRH	0.7755
UCS	Porosity, PLT, SRH,	0.7546
UCS	Density, porosity	0.7828
UCS	Density, SRH	0.7323
UCS	Density, PLT	0.7183
E	Density, porosity, PLT, SRH, P velocity	0.6406
E	Density, porosity, PLT, SRH	0.5705
E	Density, porosity, SRH	0.4912

4. Discussion

Due to the need for more accurate and easier detection of areas of exploitation layers that have unfavorable physico-mechanical properties, models to estimate UCS and E were developed based on laboratory tests. It was necessary to find a simple and sufficiently versatile model that would be based on simple, achievable tests. Tests on density, porosity and SRH can be easily evaluated, so it is understandable that they are the preferred parameters on the basis of which UCS and E are estimated.

The best model for the estimation of UCS based on single regression is the one with density as the independent variable that has a R^2 of 0.5959, and the best model of its kind to estimate E is the one with an independent variable porosity with a $R^2 = 0.5201$. More complex models can be considered more successful only if they have a higher R^2 value than the aforementioned values.

While modelling with the method of multiple regression, it was necessary to take into account that the tested independent variables used are not interdependent. According to Table 3, there is a large interdependence between density, porosity and P-velocity and so combinations of these values are not used in modelling. Table 5 shows that no combination of independent variables can achieve a higher R^2 than those achieved in single regression models. Simple models have a non-linear form and this is the reason why they are better than multiple regression models.

Neural network models have a higher estimate success rate, as expected, and the advantage of this type of model is that you are not limited in terms of the combination of predictor values. Table 6 shows that the largest R^2 values are achieved by models estimating UCS and E where the predictors include all the available values. However, since the implementation of the P-velocity test cannot be regarded as a simple test, this characteristic is omitted from the list of predictors. Therefore, it can be determined that the best estimate with the application of all essential criteria for a successful estimate is achieved by models which have density, porosity, PLT and SRH as predictors. In the case of UCS estimates, these models have a $R^2 = 0.8015$ whereas in the case of E estimates, R^2 is 0.5705.

5. Conclusion

When modelling estimates are performed in the mining industry, the possibilities of the easiest application of the model in the field must be taken into account. Therefore, single regression methods should not be neglected even though their parameters of success do not give better results than neural networks, but they have the advantage of application simplicity.

Simple regression methods that have a non-linear shape proved to be more successful than the linear generalized form of multiple regression. Therefore, future modelling using multiple regression should focus more on non-linear forms of multiple regression.

The rapid rise of computer technology makes models of neural networks more accessible, so such complex models become practically applicable and contribute to the greater security of estimated results

Acknowledgements

Dissemination process is supported by the Development Fund of the Faculty of Mining, Geology and Petroleum Engineering, University of Zagreb.

References

- [1] I. Cotman, A. Damijenić, The New Excavation Method of Exploitation of Bedding Dimension Stone Deposits, *The Mining-Geology-Petroleum Engineering Bulletin* 3 (1991) 69–76.
- [2] I. Cotman, S. Vujec, Planing and Starting Experience of Underground Exploitation of Dimension Stone in Istria, Croatia, *The Mining-Geology-Petroleum Engineering Bulletin* 10 (1998) 63–72.
- [3] I. Cotman, S. Vujec, Improved method of excavation layered deposits in underground natural stone mine, in: A. Almasi, N. J. Eftekhari (Eds.), *Mining & Sustainable Development – Teheran, Geological Survey of Iran, National Geoscience Database of Iran, 2005*, pp. 637–643.
- [4] P. Hrženjak, I. Cotman, Z. Briševac, Geotechnical investigation for designing underground natural stone mines, in: E. J. Sobczyk, J. Kicki, (Eds.), *21th World Mining Congress & Expo 2008, Krakow, New Challenges and Visions for Mining, CRC Press Balkema, London, 2008*. 197–206.
- [5] Z. Briševac, T. Kujundžić, Models to estimate brazilian indirect tensile strength of limestone in saturated state, *The Mining-Geology-Petroleum Engineering Bulletin* 31 (2016) 59–67.
- [6] V. Palchik, Y.H. Hatzor, Influence of porosity on tensile and compressive strength of porous chalks. *Rock Mechanics and Rock Engineering*, 37 (2004) 331–341.
- [7] A. Tugrul, The effect of weathering on pore geometry and compressive strength of selected rock types from Turkey, *Engineering Geology* 75 (2004) 215–227.
- [8] G.P. Tziailas, G. Tsiambaos, H. Saroglou, Determination of rock strength and deformability of intact rocks, *Electronic Journal of Geotechnical Engineering* 14 G (2009) 1–12.
- [9] S. Yagiz, Predicting uniaxial compressive strength, modulus of elasticity and index properties of rocks using the Schmidt hammer, *Bulletin of Engineering Geology and the Environment* 68 (2009) 55–63.
- [10] Z.A. Moradian, M. Behnia, Predicting the uniaxial compressive strength and static young's modulus of intact sedimentary rocks using the ultrasonic test, *International Journal of Geomechanics* 9 (2009) 14–19.
- [11] A. Manouchehrian, M. Sharifzadeh, R.H. Moghadam, Application of artificial neural networks and multivariate statistics to estimate UCS using textural characteristics, *International Journal of Mining Science and Technology* 22 (2012) 229–236.
- [12] S. Dehghan, G. Sattari, C.S. Chehreh, M.A. Aliabadi, Prediction of uniaxial compressive strength and modulus of elasticity for Travertine samples using regression and artificial neural Networks, *Mining Science and Technology* 20 (2010) 41–46.
- [13] C. Gokceoglu, K. Zorlu, A fuzzy model to predict the uniaxial compressive strength and the modulus of elasticity of a problematic rock, *Engineering Applications of Artificial Intelligence* 17 (2004) 61–72.
- [14] M. Karakus, B. Tutmez, Fuzzy and Multiple Regression Modelling for Evaluation of Intact Rock Strength Based on Point Load, Schmidt Hammer and Sonic Velocity, *Rock Mechanics and Rock Engineering* 39 (2006) 45–57.
- [15] I. Yilmaz, G. Yuksek, Prediction of the strength and elasticity modulus of gypsum using multiple regression, ANN, and ANFIS models, *International Journal of Rock Mechanics and Mining Sciences* 46 (2008) 803–810.
- [16] S. Dehghan, G. Sattari, C.S. Chehreh, M.A. Aliabadi, , Prediction of uniaxial compressive strength and modulus of elasticity for Travertine samples using regression and artificial neural Networks, *Mining Science and Technology* 20 (2010) 41–46.
- [17] ISRM, Suggested methods for determining water content, porosity, density, absorption and related properties and swelling and slake-durability index properties, Part 1: suggested method for determination of the water content of a rock sample; suggested method for porosity/density determination using saturation and caliper techniques. *Int. J. Rock Mech. Min. Sci. Geomech. Abst.* 16 (1979) 141–156.
- [18] ISRM, Suggested methods for determining the uniaxial compressive strength and deformability of rock materials, *Int. J. Rock Mech. Min. Sci. Geomech. Abst.* 16 (1979) 135–140.
- [19] ISRM, Suggested method for determining sound velocity, *Int. J. Rock Mech. Min. Sci. Geomech. Abst.* 15–2 (1978) 53–58.
- [20] ISRM, Suggested method for determining point load strength. *Int. J. Rock Mech. Min. Sci. Geomech. Abst.* 22 (1985) 51–60.
- [21] A. Aydin, ISRM Suggested Method for Determination of the Schmidt Hammer Rebound Hardness: Revised Version, *The ISRM Suggested Methods for Rock Characterization, Testing and Monitoring*, 2014, pp 25–33.
- [22] P. Hrženjak, A. Jaguljnjak-Lazarević, Z. Briševac, The research of stability for underground chambers of the quarry of natural stone in the exploitation field „Kanfanar-jug“, *Technical Study, Faculty of Mining, Geology and Petroleum Engineering, Zagreb*, 2014.
- [23] J.D. Evans, *Straightforward Statistics for the Behavioral Sciences*, Cole Publishing Co., Pacific Grove, 1996.
- [24] R.J. Dunham, Classification of carbonate rocks according to depositional texture, in: W. E. Ham, (Eds.), *Classification of carbonate rocks: American Association of Petroleum Geologists Memoir*, 1962, pp. 108–121.
- [25] Z. Briševac, P. Hrženjak, R. Buljan, Models for estimating uniaxial compressive strength and elastic modulus, *68-1 GRAĐEVINAR* (2016) 19–28.